

Is Δ_π -gap-only superconductivity possible in $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ alloys ?

P. Jiji Thomas Joseph and Prabhakar P. Singh

Department of Physics, Indian Institute of Technology Bombay, Mumbai - 400076, India

Using density-functional-based method, we study the $\mathbf{k}$ -resolved σ - and π -band holes in $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ alloys. We find that the calculated profiles of the loss of σ - and π -band holes in these two systems as a function of impurity concentration are in qualitative agreement with experiments, as expected. We also describe its implications *vis-a-vis* superconductivity in $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$.

The surprising discovery of superconductivity at 40 K in a simple metal MgB_2 [1] a few years ago continues to test the details of the microscopic picture offered by Bardeen-Cooper-Schrieffer theory of superconductivity and its extensions thereof. Generally, it is agreed that in MgB_2 (i) there are two superconducting gaps [2, 3, 4, 5, 6, 7, 8] Δ_σ and Δ_π of 7 meV and 2 meV, respectively, (ii) the two gaps arise from the holes in the B p_σ and p_π bands [8, 9, 10, 11, 12, 13, 14], (iii) the holes in the B p_σ and p_π bands couple strongly to the in-plane E_{2g} phonon mode [14, 15, 16, 17], and (iv) the coupling is particularly strong along Γ - A direction and around M point in the hexagonal Brillouin zone [18].

To gain further insight into the role played by the holes of the B p_σ and p_π bands in deciding the superconducting properties as well as the relative strengths of the two gaps Δ_σ and Δ_π in MgB_2 , recently, there has been a concerted effort to examine the various superconducting properties of *doped* MgB_2 . In particular, the Al doping at the Mg site and the C doping at the B site in MgB_2 [19, 20, 21, 22, 23, 24, 25, 26, 27, 28, 29] are expected to fill up the holes in the B p_σ and p_π bands which, in turn, would affect the two gaps Δ_σ and Δ_π . Understanding the changes in the superconducting properties of $Mg_{1-x}Al_xB_2$ as a function of Al concentration x and of $Mg(B_{1-y}C_y)_2$ as a function of C concentration y would provide a more detailed information about the electron-phonon and the electron-electron interactions in these alloys.

Experimentally, in $Mg_{1-x}Al_xB_2$ the superconducting transition temperature T_c as well as the gap Δ_σ are found to decrease with increasing Al concentration [19, 21, 22, 30, 31]. The change in the gap Δ_π is relatively small up to $x \sim 0.7$ at which the superconductivity vanishes in $Mg_{1-x}Al_xB_2$. However, in $Mg(B_{1-y}C_y)_2$ the T_c [27, 32, 33, 34, 35, 36, 37, 38, 39, 40] and the Δ_σ decrease rapidly as a function of C concentration with superconductivity vanishing at around $y \sim 0.15$. The change in Δ_π , once again, is found to be minimal in $Mg(B_{1-y}C_y)_2$ [28, 38, 40, 41, 42].

Most of the previous theoretical studies [43, 44, 45, 46, 47, 48, 49, 50, 51] of $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ used virtual-crystal approximation [43, 47, 48, 50, 51] or supercell approach [46], having limited predictive capability, to describe the chemical disorder in the Mg sub-

lattice and the B sub-lattice respectively. An accurate and reliable description of chemical disorder, provided by coherent-potential approximation, has been used previously in the study of $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ [44, 45, 49] but these studies provided either $\mathbf{k}$ -integrated information or were inconclusive.

Since many of the superconducting properties of MgB_2 and its alloys $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ are crucially dependent on their *normal state* electronic structure [8, 15, 17, 52, 53, 54], especially along Γ - A direction and M point of the hexagonal Brillouin zone (BZ), we study the changes in $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ alloys as a function of Al and C concentrations respectively, using $\mathbf{k}$ -resolved Bloch spectral function $A(\mathbf{k}, E)$ [55, 56] and B and C $p_{x(y)}$ and p_z densities of states. It is expected that with increasing Al and C concentrations the holes in the respective alloys would get gradually filled up. However, not surprisingly, the way the holes are filled up in $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ alloys make the two systems quite different from each other as detailed below.

In this Letter we show that in $Mg_{1-x}Al_xB_2$ (i) the σ -band holes along Γ - A get annihilated by $x \sim 0.8$ with the holes at Γ vanishing first at $x \sim 0.5$, and (ii) the π holes at M vanish by $x \sim 0.7$. However, in $Mg(B_{1-y}C_y)_2$ (i) the σ -band holes along Γ - A deplete rapidly and vanish beyond $y \sim 0.25$ with the holes at A vanishing first, and (ii) the π -band holes at M as well as σ -band holes at A reduce substantially beyond $y \sim 0.1$. Before we discuss our results, we briefly describe the details of our calculations.

The normal metal electronic structure of the disordered alloys $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ are calculated using the Korringa-Kohn-Rostoker (KKR) Green's function method formulated in the atomic sphere approximation (ASA) [57, 58], which has been corrected by the use of both the muffin-tin correction for the Madelung energy, needed for obtaining an accurate description of ground state properties in the ASA [59], and the multipole moment correction to the Madelung potential and energy which significantly improves the accuracy by taking into consideration the non-spherical part of polarization effects [60]. Chemical disorder was taken into account by means of coherent-potential approximation (CPA) [61]. The exchange and correlation were included

within the local density approximation (LDA) using the Perdew-Wang parameterization of the many-body calculations of Ceperley and Alder [62]. During the self-consistent procedure the reciprocal space integrals were calculated by means of 2299 $\mathbf{k}$ -points in the irreducible part of the hexagonal BZ, while the energy integrals were evaluated on a semicircular contour in the complex energy plane using 24 energy points distributed in such a way that the sampling near the Fermi energy was increased. When calculating the density of states the number of $\mathbf{k}$ -points was increased to 6075. The atomic sphere radii of Mg and B were kept as 1.294 and 0.747, respectively of the Wigner-Seitz radius. The sphere radii of the substituted Al and C were kept the same as that of Mg and B respectively. The overlap volume resulting from the blow up of the muffin-tin spheres was approximately 10%, which is reasonable within the accuracy of the approximation [63]. The charge self-consistency iterations were accelerated using the Broyden's mixing scheme [64], the CPA self consistency was accelerated using the prescription of Abrikosov *et al* [65]. The calculations for $Mg_{1-x}Al_xB_2$ for $0 \leq x \leq 1$ and $Mg(B_{1-y}C_y)_2$ for $0 \leq y \leq 0.3$ were carried out at experimentally obtained lattice parameters of these alloys, assuming a rigid underlying lattice. The effects of local lattice-relaxation as well as any possible short-range ordering effects are not considered. Our results for $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ are analyzed in terms of Bloch spectral density, $A(\mathbf{k}, E)$ [55] and the B and C p densities of states.

In general, electron doping of MgB_2 by substituting Al at the Mg sub-lattice or C at the B sub-lattice can have three important effects, (i) the outward movement of the Fermi energy due to addition of electrons, (ii) disorder-induced broadening of peaks in $A(\mathbf{k}, E)$, and (iii) redistribution of states due to hybridization. If the disorder and hybridization-related effects are negligible then electron doping can be well described by a rigid-band-like picture, where E_F is shifted up using MgB_2 densities of states until the added electrons are accommodated. In such a case, the σ - and π -band holes would gradually get filled up as a function of electron doping. Thus, in the rigid-band picture the σ - and π -band-hole-dependent superconducting properties of MgB_2 alloys would be similar as a function of electron doping. However, if the disorder and the hybridization lead to significant modifications of the σ - and π -band holes then the electronic properties of both the normal and the superconducting states of MgB_2 alloys would depend on the details of electron doping rather than just the electron count. Experimentally, as outlined in earlier paragraphs, the σ - and π -band-hole-dependent properties of the two alloys, $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$, are found to differ significantly from each other as a function of Al and C concentrations, underscoring the importance of disorder and hybridization effects in these alloys, in particular on σ -

and π -band holes. Therefore, in the following, we primarily focus on the changes in the states close to E_F , which happen to be the p_σ states at Γ and A points and p_π state at M point of the hexagonal BZ.

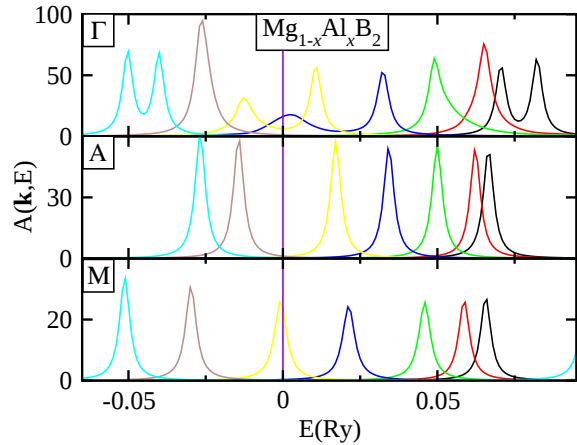


Figure 1: The Bloch spectral function $A(\mathbf{k}, E)$ of $Mg_{1-x}Al_xB_2$ alloys calculated at Γ (top panel), A (middle panel) and M (bottom panel) points of the hexagonal Brillouin zone using the KKR-ASA-CPA method for x equal to 0 (black), 0.1 (red), 0.3 (green), 0.5 (blue), 0.7 (yellow), 0.9 (brown) and 1 (cyan), respectively. The vertical line through the energy zero represents the Fermi energy.

The most important result of the present work for $Mg_{1-x}Al_xB_2$ alloys is shown in Fig.1, where we show the Bloch spectral function $A(\mathbf{k}, E)$ as a function of x for $0 \leq x \leq 1$ at Γ , A and M points of the hexagonal BZ in a limited energy window (± 0.1 Ry) around Fermi energy E_F . Along Γ - A , the doubly degenerate B p_σ states in $Mg_{1-x}Al_xB_2$ alloys move closer to E_F with increasing Al concentration from $x = 0.1$ to $x = 0.70$, indicating a decrease in σ -band holes and subsequently, weakening of electron-phonon coupling along this direction. We also find that for $x \sim 0.5$, the peak in $A(\mathbf{k}, E)$ is at E_F indicating some topological changes in the Fermi surface of the alloy. By $x = 0.90$, the B p_σ states at A are well inside E_F , resulting in the annihilation of all the p_σ hole states along Γ - A . Thus, we should not expect σ -band-hole-based superconductivity beyond $x = 0.80$. We also find that the Mg -derived antibonding s -state (Γ_6) moves closer to the p_σ state for intermediate concentrations but separates out for $x = 1.0$.

The B p_π hole states at M in $Mg_{1-x}Al_xB_2$ alloys get gradually annihilated with increasing Al concentration from $x = 0.1$ to $x = 0.50$. We find that the $A(\mathbf{k}, E)$ peak corresponding to p_π states crosses E_F at a lower x than the p_σ states at A point. As the contribution to the electron-phonon coupling responsible for π -band superconductivity comes from M and other similar points in the BZ, a Δ_π -gap-only superconductivity seems unlikely in $Mg_{1-x}Al_xB_2$ alloys. However, it does not preclude a crossover from a σ to π dominated superconductivity

[51].

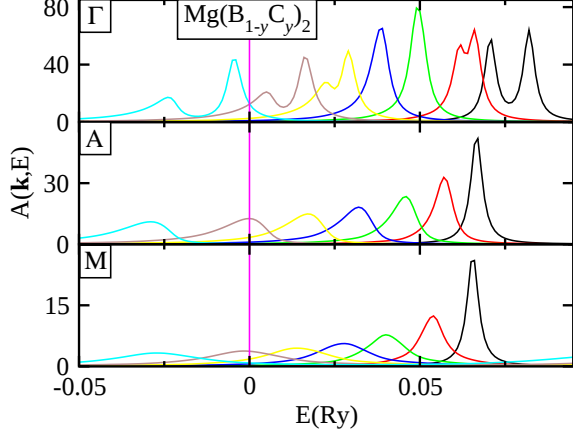


Figure 2: The Bloch spectral function $A(\mathbf{k}, E)$ of $Mg(B_{1-y}C_y)_2$ alloys calculated at Γ (top panel), A (middle panel) and M (bottom panel) points of the hexagonal Brillouin zone using the KKR-ASA-CPA method for y equal to 0 (black), 0.05 (red), 0.1 (green), 0.15 (blue), 0.2 (yellow), 0.25 (brown) and 0.3 (cyan), respectively. The vertical line through the energy zero represents the Fermi energy.

In Fig. 2 we show the Bloch spectral function $A(\mathbf{k}, E)$ of $Mg(B_{1-y}C_y)_2$ alloys as a function of y for $0 \leq y \leq 0.3$ at Γ , A and M points around Fermi energy. We find that with increasing C concentration from $y = 0.05$ to $y = 0.2$ the p_σ states along Γ - A move towards E_F as well as get redistributed on the energy scale due to disorder and hybridization. In fact, in the range $y = 0.1$ to $y = 0.15$, we find substantial reduction in p_σ states around A point. Since the electron-phonon coupling is stronger near A point, the loss of p_σ states should dramatically affect the σ -band superconductivity. Similar to the reduction of p_σ states along Γ - A , the p_π hole states at M point in $Mg(B_{1-y}C_y)_2$ alloys are drastically reduced by $y = 0.1$. Here, it must be noted that the reduction in σ - and π -band holes in $Mg_{1-x}Al_xB_2$ with increasing Al concentration is mostly due to the upward movement of the Fermi energy. In contrast, disorder and hybridization play a dominant role in reducing the σ - and π -band holes in $Mg(B_{1-y}C_y)_2$ alloys.

The changes in the B p_σ and p_π hole states in $Mg_{1-x}Al_xB_2$ as a function of Al concentration and in $Mg(B_{1-y}C_y)_2$ as a function of C concentration can be seen more clearly in their respective partial densities of states as shown in Fig. 3. In $Mg_{1-x}Al_xB_2$ alloys the B $p_{x(y)}$ hole states decrease steadily as a function of x , vanishing for $x \sim 0.8$ as shown in Fig. 3. Thus, as stated earlier in the context of $A(\mathbf{k}, E)$, we should not expect σ -band-hole-based superconductivity beyond $x = 0.80$ $Mg_{1-x}Al_xB_2$. However, the decrease in B p_z hole states with increasing x is not as much. Even for $x = 1.0$, there are B p_z hole states available in $Mg_{1-x}Al_xB_2$ as shown in Fig.3 but it does not sustain Δ_π -gap-only supercon-

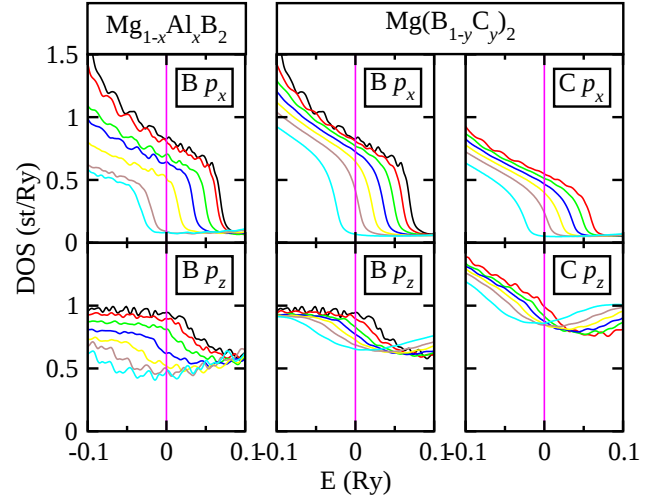


Figure 3: The atom (B and C) and orbital ($p_{x(y)}$ and p_z) projected density of states (DOS) in $Mg_{1-x}Al_xB_2$ (left panels) and $Mg(B_{1-y}C_y)_2$ (middle and right panels) alloys calculated using the KKR-ASA-CPA method for $x(y)$ equal to 0(0) (black), 0.1(0.05) (red), 0.3(0.1) (green), 0.5(0.15) (blue), 0.7(0.2) (yellow), 0.9(0.25) (brown) and 1(0.3) (cyan), respectively. The vertical line through the energy zero represents the Fermi energy.

ductivity.

For $Mg(B_{1-y}C_y)_2$ alloys, our results show that $p_{x(y)}$ and p_z densities of states of both B and C behave similarly with increasing C concentration, as can be seen from Fig. 3. By $y \sim 0.25$, most of the $p_{x(y)}$ hole states of B and C have moved inside E_F . As pointed out above, in $Mg(B_{1-y}C_y)_2$ alloys with the addition of C those σ -band holes are lost first which couple to the phonons more strongly which may lead to a loss of superconductivity in spite of having some $p_{x(y)}$ hole states of B and C . The changes in the p_z hole states are minimal in $Mg(B_{1-y}C_y)_2$, with a slight increase in the hole states for higher C concentrations.

We like to point out that the approximations used in the present work, namely the use of spherically symmetric potential to describe the effective one-electron interaction and the overlapping atomic spheres to fill the space, are expected to affect some numerical aspects of the present work. The use of optimized lattice constants is expected to similarly affect the present work, especially in $Mg(B_{1-y}C_y)_2$ alloys for $y \geq 0.2$ because for these concentrations we have used the lattice constants corresponding to $y = 0.15$. However, our results for MgB_2 and AlB_2 are consistent with the more accurate, full-potential results, and since the coherent-potential approximation is known to describe the effects of disorder reliably, we expect our intermediate-concentration-results to be robust and qualitatively correct.

In conclusion, we have studied the $\mathbf{k}$ -resolved σ - and π -band holes in $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ alloys.

The calculated profiles of the loss of σ - and π -band holes in these two systems as a function of impurity concentration are expected to be in qualitative agreement with the experiments. We have also described its implications *vis-a-vis* superconductivity in $Mg_{1-x}Al_xB_2$ and $Mg(B_{1-y}C_y)_2$ alloys.

One of us (PJTJ) would like to thank Dr. Andrei Ruban for providing the KKR-ASA code. Discussions with Dr. Igor Mazin on the electronic structure properties of MgB_2 is gratefully acknowledged.

-
- [1] J. Nagamatsu *et al.*, Nature 410, 63 (2001)
 - [2] S. Souma *et al.*, Nature 423, 65 (2003)
 - [3] M. Iavarone *et al.*, Phys. Rev. Lett. 89, 187002 (2002)
 - [4] F. Bouquet *et al.*, Phys. Rev. Lett. 89, 257001 (2002)
 - [5] S. Tsuda *et al.*, Phys. Rev. Lett. 91, 127001 (2003)
 - [6] P. Szabo *et al.*, Phys. Rev. Lett. 87, 137005 (2001)
 - [7] H. Schmidt *et al.*, Phys. Rev. Lett. 88, 127002 (2002)
 - [8] A. Y. Liu *et al.*, Phys. Rev. Lett. 87, 087005 (2001)
 - [9] H. Schmidt *et al.*, Phys. Rev. B 63, 220504 (2001)
 - [10] G. Karapetrov *et al.*, Phys. Rev. Lett. 86, 4374 (2001)
 - [11] H. J. Choi, D. Roundy *et al.*, Nature 418, 758 (2002)
 - [12] W. L. McMillan, Phys. Rev. 175, 537 (1968)
 - [13] P. Seneor *et al.*, Phys. Rev. B 65, 012505 (2001)
 - [14] C. Joas *et al.*, Phys. Rev. B 65, 132518 (2002)
 - [15] J. Kortus *et al.*, Phys. Rev. Lett. 86, 4656 (2001)
 - [16] H. J. Choi, D. Roundy *et al.*, Phys. Rev. B 66, 020513 (2002)
 - [17] K.-P. Bohnen *et al.*, Phys. Rev. Lett. 86, 5771-5774 (2001)
 - [18] P. P. Singh, Phys. Rev. B 67, 132511 (2003)
 - [19] J. S. Slusky *et al.*, Nature 410, 343 (2001)
 - [20] S. Agrestini *et al.*, J. Phys.: Condens. Matter 13, 11689 (2001)
 - [21] J. Y. Xiang *et al.*, Phys. Rev. B 65, 214536 (2002)
 - [22] J. Q. Li *et al.*, Phys. Rev. B 65, 132505 (2002)
 - [23] P. Postorino *et al.*, Phys. Rev. B 65, 020507 (2001)
 - [24] S. Margadonna *et al.*, Phys. Rev. B 66, 014518 (2002)
 - [25] G. Papavassiliou *et al.*, Phys. Rev. B 66, 140514 (2002)
 - [26] A. Bianconi *et al.*, Phys. Rev. B 65, 174515 (2002)
 - [27] R. A. Ribeiro *et al.*, Physica C 385, 16 (2003)
 - [28] H. Schmidt *et al.*, Phys. Rev. B 68, 060508 (2003)
 - [29] R. A. Ribeiro *et al.*, Physica C 384, 227 (2003)
 - [30] J. Karpinski *et al.*, Phys. Rev. B 71, 174506 (2005)
 - [31] M. Putti *et al.*, Phys. Rev. B 71, 144505 (2005)
 - [32] M. Paranthaman *et al.*, Physica C 355, 1 (2001)
 - [33] W. Mickelson *et al.*, Phys. Rev. B 65, 052505 (2002).
 - [34] S. M. Kazakov *et al.*, cond-mat/0405060
 - [35] T. Takenobu *et al.*, Phys. Rev. B 64, 134513 (2001)
 - [36] T. Masui *et al.*, Phys. Rev. B 70, 024504 (2004)
 - [37] R. H. T. Wilke *et al.*, Phys. Rev. Lett. 92, 217003 (2004)
 - [38] G. A. Ummarino *et al.*, Phys. Rev. B 71, 134511 (2005)
 - [39] A. V. Sologubenko *et al.*, Phys. Rev. B 71, 020501 (2005)
 - [40] Z. Holanová *et al.*, Phys. Rev. B 70, 064520 (2004)
 - [41] S. M. Kazakov *et al.*, Phys. Rev. B 71, 024533 (2005)
 - [42] P. Samuely *et al.*, Phys. Rev. B 68, 020505 (2003)
 - [43] O. de la Peña *et al.*, Phys. Rev. B 66, 012511 (2002)
 - [44] P. P. Singh, Physica C 382, 381 (2002)
 - [45] P. P. Singh, Solid State Commun. 127, 271 (2003)
 - [46] A. Bussmann-Holder and A. Bianconi, Phys. Rev. B 67, 132509 (2003)
 - [47] G. Profeta *et al.*, Phys. Rev. B 68, 144508 (2003)
 - [48] G. A. Ummarino *et al.*, Physica C 407, 121 (2004)
 - [49] D. Kasinathan *et al.*, cond-mat/0409563
 - [50] J. Kortus *et al.*, Phys. Rev. Lett. 94, 027002 (2005)
 - [51] L. D. Cooley *et al.*, Phys. Rev. Lett. 95, 267002 (2005)
 - [52] I. I. Mazin *et al.*, Phys. Rev. Lett. 89, 107002 (2002)
 - [53] T. Yildirim *et al.*, Phys. Rev. Lett. 87, 037001 (2001)
 - [54] P. P. Singh, Phys. Rev. Lett. 87, 087004 (2001)
 - [55] J. S. Faulkner and G. M. Stocks Phys. Rev. B 21, 3222 (1980)
 - [56] J. S. Faulkner, Prog. Mater. Sci. 27, 1 (1982)
 - [57] I. Turek *et al.*, Electronic structure of disordered alloys, surfaces and interfaces, (Kluwer Academic Publishers, Boston, 1997)
 - [58] Electrons in disordered metals and at metallic surfaces, P. Phariseau, B. L. Gyorffy and L. Scheire, eds. New York, Plenum Press (1979)
 - [59] N. E. Christensen and S. Satpathy, Phys. Rev. Lett. 55, 600 (1985)
 - [60] A. V. Ruban and H. L. Skriver Computational Materials Science, 15, 119 (1999)
 - [61] P. Soven Phys. Rev. 156, 809 (1967)
 - [62] J. P. Perdew and Y. Wang, Phys. Rev. B 45, 13244 (1992)
 - [63] The LMTO method, Muffin tin orbitals and electronic structure, Hans. L. Skriver, Springer-Verlag (1984)
 - [64] D. D. Johnson, Phys. Rev. B 38, 12807-12813 (1988)
 - [65] Abrikosov *et al.*, Phys. Rev. B 56, 9319 (1997)
 - [66] A. Bharathi *et al.*, Physica C 370, 211 (2002)
 - [67] M. Avdeev *et al.*, Physica C 387, 301 (2003)